

# **LUCCHINI** 2367 ESR

**SPECIAL HOT WORK TOOL STEEL  
VERY HIGHLY RESISTANT TO THERMAL  
FATIGUE AND HIGH TEMPERATURE WEAR  
IN ESR QUALITY**

**FORGING  
VALUES  
IN TOOL  
STEELS**

IMPROVEMENT  
COURAGE  
PEOPLE  
PASSION  
SPIRIT  
GROUP  
CUSTOMER  
SUCCESS

GROUP  
**LUCCHINI** RS

## General characteristics

---

Lucchini 2367 ESR is a special high alloyed Chromium- Molybdenum-Vanadium Hot Work Tool steel designed for the manufacture of dies, moulds, punches and other tools subjected to high working temperatures that need very highly resistant to thermal fatigue and high temperature wear.

If subjected to suitable hardening, followed by at least two suitable tempers, LUCCHINI 2367 ESR can reach a hardness of 52 HRC without strongly affecting the toughness.

In order to improve further the mechanical characteristics of the surface, LUCCHINI 2367 ESR can be coated with PVD or PA/ CVD methods. Alternatively it can be subjected to nitriding; this allows a hardness value of the nitrided layer up to about 900-1000 HV.

Thanks to its quasi-isotropic properties of ESR quality, LUCCHINI 2367 ESR represents also one of the most important tough options, for highly resistant plastic moulds that need very high pressure strength, excellent resistance to abrasion, also in combination with different surface coatings, and improved toughness in the meantime.

## Delivery conditions

---

LUCCHINI 2367 ESR is supplied in annealed condition in dimensional range up to 500 mm thickness.

The surface hardness value is lower than 220 HB, guaranteeing a good machinability.

## Main features

---

- high resistance to thermal shock and to heat cracking;
- excellent mechanical characteristics in hot condition;
- excellent toughness in hot condition;
- resistance to temper;
- excellent machinability.

## Main application

---

- dies for aluminium die-casting;
- dies subjected to low pressure;
- chill moulds for gravity casting;
- containers for die-casting presses;
- dies for aluminium extrusion;
- extrusion press blocks;
- sleeves for extrusion presses;
- injection moulds.

## Chemical analysis

	Range	C [%]	Si [%]	Mn [%]	Cr [%]	Mo [%]	Ni [%]	V [%]
<b>LUCCHINI 2367 ESR</b> Alloying [% in weight]	min	0,32	0,10	0,30	4,80	2,80	-	0,40
	max	0,40	0,30	0,50	5,50	3,20	-	0,70

Comparison with international classifications:

**W. Nr. 1.2367**

**DIN EN ISO4957 X38CrMoV5-3**

**NADCA GRADE C**

## Physical and mechanical properties

### Main physical properties

<b>LUCCHINI 2367 ESR</b>	20°C	400°C	600°C
Young modulus E [MPa]	210	175	166
Coefficient of linear thermal expansion $\alpha$ [10 <sup>-6</sup> /K]	-	12,1	12,9
Thermal conductivity $\lambda$ [W/mK]	25,8	27,2	31,4


### Main mechanical properties

<b>LUCCHINI 2367 ESR</b>	400°C	500°C	600°C
Ultimate tensile strength UTS [MPa]	1240	1060	760
Yield strength YS [MPa]	1020	850	520


The above mentioned are average values of a sample hardened at 1020 °C, quenched and tempered to achieve hardness value of 44 HRC

### Microstructure

The main microstructure of LUCCHINI 2367 ESR consist of a ferritic matrix with a homogeneous distribution of spheriodized carbides.

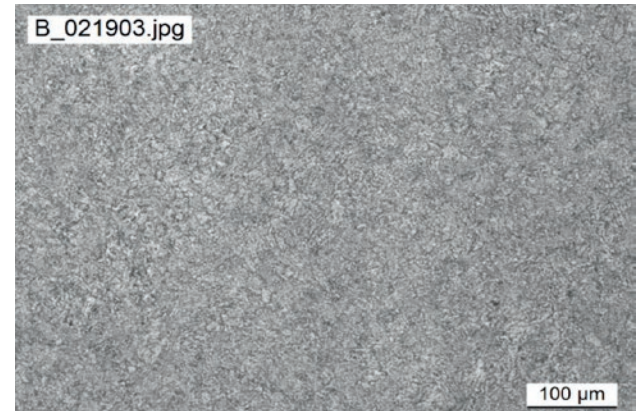


100x

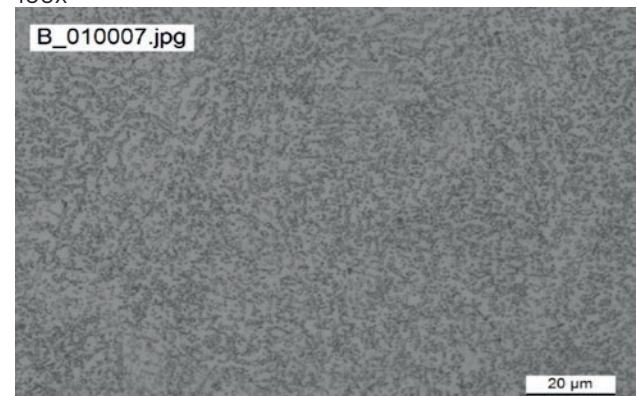

500x

## Surface hardness vs tempering temperature


Tempering curve of a sample austenitized at 1020°C. The diagram shows values obtained after the second tempering; the first tempering is performed at 550°C.

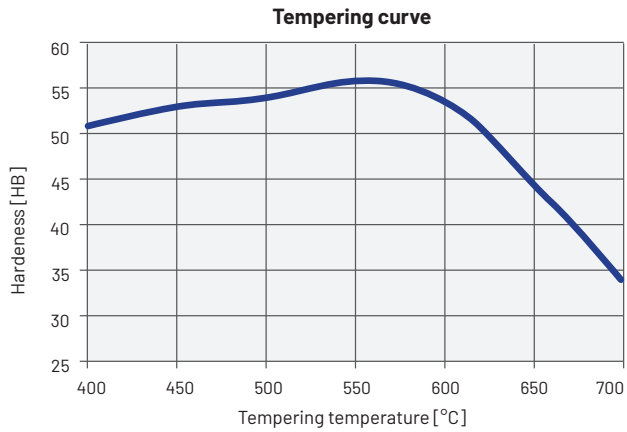

## Heat treatment

Lucchini 2367 ESR is supplied in annealed condition with a hardness value below 220 HB. Heat treatment shall be carried out using the parameters recommended and given below.

### Continuous cooling transformation curve (CCT)

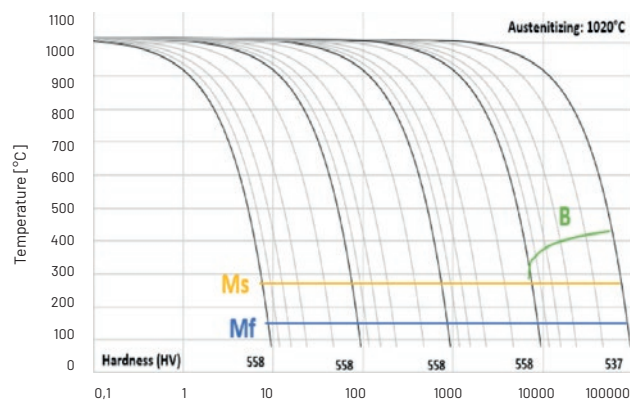

### Soft annealing

<b>Heating</b>	Max 50°C/h
<b>Suggested temperature</b>	850°C
<b>Soaking time</b>	120 min from the temperature's settlement
<b>Cooling</b>	Slow cooling in furnace (20°C/h)

Soft annealing is useful to improve machinability reducing hardness at 220 HB.

### Stress relieving

<b>Heating</b>	Max 100°C/h
<b>Suggested temperature</b>	Annealed condition: 650°C QT condition: 50°C lower than the last tempering
<b>Soaking time</b>	120 min from the temperature's settlement
<b>Cooling</b>	Slow cooling in furnace (20°C/h)

We strongly recommend to perform the stress relieving:

- After rough machining in order to minimize distortions and avoid quenching cracks by hardening treatment;
- After the finish machining, before the very first sampling, to avoid possible damages to cavity surface and sub-surface caused by not optimized hard milling.

### Hardening

We suggest to carry out the hardening process on material supplied in the annealed condition and to temper it immediately afterwards.

Hardening should be carried out after the material pre-heating according to the following table.

<b>Heating</b>	Max 150°C/h
<b>First pre-heating temperature</b>	400°C
<b>Soaking time</b>	25 min / 25 mm in thickness or ( $T_{SURFACE} - T_{CORE}$ ) < 90°C

<b>Heating</b>	Max 150°C/h
<b>Second pre-heating temperature</b>	600°C
<b>Soaking time</b>	20 min / 25 mm in thickness or ( $T_{SURFACE} - T_{CORE}$ ) < 90°C

<b>Heating</b>	Max 150°C/h
<b>Third pre-heating temperature</b>	800°C
<b>Soaking time</b>	20 min / 25 mm in thickness or ( $T_{SURFACE} - T_{CORE}$ ) < 90°C

The aim of the first pre-heat at 400 °C is to eliminate stresses caused by machining: if stress relieving is performed earlier, this step could be avoided.

The following pre-heating cycles at 600 °C and 800 °C are necessary to homogenize the temperature of the piece. We recommend an heating rate of 150 °C/h max.

The time of the different stages of pre-heating is calculated on the basis of the thickness of the piece and the temperature, as described in the above attached table.

Alternatively, the time can be adjusted on the basis of the difference between the internal temperature ( $T_{CORE}$ ) and the Surface temperature ( $T_{SURFACE}$ ) of the piece, measured by two thermocouples.

After the third pre-heating at 800°C, the austenitizing temperature should be reached as quickly as possible and maintained for 30 min from when ( $T_{SURFACE} - T_{CORE}$ ) < 15 °C or on the basis of the following formula:

$$t = (x + 39) / 2$$

t = soaking time [min]  
x = thickness [mm]

<b>Heating temperature</b>	Max 150°C/h
<b>Soaking time</b>	t=(x+39)/2 or 30 min from ( $T_{SURFACE} - T_{CORE}$ ) < 15°C
<b>Cooling</b>	Air, vacuum cooling, salt bath, polymer

## Tempering

It is recommended to set the temperature of the first tempering at 550°C, close to the secondary peak hardness.

The temperature of the second tempering must be set according to the required mechanical properties and must be higher than the temperature of the first tempering.

The soaking time for the first and the second tempering are calculated by the following empirical formula:

$$t' = t'' = 0,8 x + 120$$

t' = t'' = soaking time [min]  
x = thickness [mm]

A third tempering at 30-50 °C less than the maximum temperature previously used will work as a stress relieving process.

Tempering at a temperature between 400 and 550 °C is not advisable, as it may reduce the material toughness. Tempering at a temperature lower than 200 °C should not be carried out.

The soaking time for the third tempering is calculated by the following empirical formula:

$$t''' = 0,8 x + 120$$

t''' = soaking time [min]  
x = thickness [mm]

<b>First tempering temperature</b>	550°C
<b>Soaking time</b>	t' = 0,8 x + 120
<b>Cooling</b>	Still air

<b>Second tempering temperature</b>	Based on mechanical properties required
<b>Soaking time</b>	t'' = 0,8 x + 120
<b>Cooling</b>	Still air

<b>Third tempering temperature</b>	30-50 °C less than the maximum temperature previously used
<b>Soaking time</b>	t''' = 0,8 x + 180
<b>Cooling</b>	Still air

## **Chrome plating**

LUCCHINI 2367 ESR can be Chrome plated in order to enhance the mechanical characteristics on the surface.

In order to prevent Hydrogen embitterment, within 4 hours of Chrome plating it is advisable to carry out heat treatment at 200 °C for about 4 hours.

## **Nitriding**

LUCCHINI 2367 ESR is suitable for ionic and gas nitriding. This treatment is very useful for moulds subjected to extremely stressful applications.

The increase of the surface hardness, following nitriding, extends the component life cycle.

Up-to-date nitriding procedures allow to minimize the dimensional variation of the piece.

Other properties can be deeper analysed against specific Customer request: please contact our Metallurgy Department.

## **Polishing and photo-engraving**

---

Lucchini 2367 ESR is the suitable material when polishing and photoengraving are needed. Thanks to its integrated manufacturing process, those material manufactured by Lucchini RS are characterized by a high degree of purity.

**Polishing for graining: 4 Excellent**

**Suitability for medium gloss polishing: 4 Excellent**

**Suitability for mirror polishing: 4 Excellent**

**Suitability for engraving: 4 Excellent**

Rating scale:

**4 Excellent** – **3 Very good** – **2 Good** – **1 Normal** – **0 Unsuitable**

## The advantages of the ESR technology

The ESR (Electro-Slag-Melting) manufacturing technology offers the following advantages:




- increase of material toughness;
- high micro-cleanness level;
- total isotropy of the material;
- very low segregation level.

The ESR process is based on ingot remelting, through a traditional VD (vacuum degassing) process, using a particular copper ingot mould that contains basic slag.

The ingot is remelted in a way that the liquid metal passes through the slag, which acts as a filter and retains the inclusions.

The process of solidification inside the ingot mould is faster than in a traditional process.

The result is homogeneous and isotropic steel.

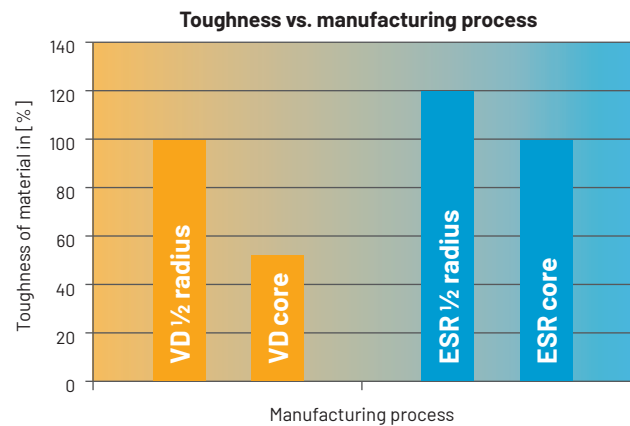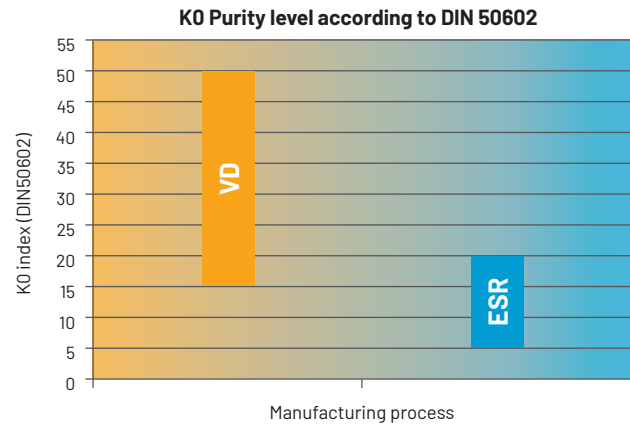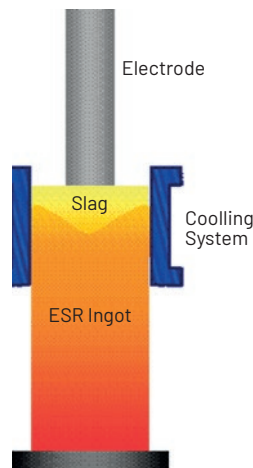

Thanks to the ESR process, LUCCHINI 2367 ESR satisfies the most difficult requirements in terms of toughness and suitability to polishing. It is suitable for the manufacture of moulds subjected to mirror polishing and to high mechanical stress.



## Guidance for machining

The following parameters are approximate only and must be adjusted to the specific application and machine tool.

### Turning

Type of insert	Rough machining		Finish machining	
	P20-P40 coated	HSS	P10-P20 coated	Cermet
$V_c$ cutting speed [m/min]	150 ÷ 190	(*)	190 ÷ 230	260 ÷ 320
$a_r$ cutting depth [mm]	5	(*)	< 1	< 0,5

### Milling

Type of insert	Rough machining		
	P25-P35 not coated	P25-P35 coated	HSS
$V_c$ cutting speed [m/min]	120 ÷ 140	160 ÷ 180	(*)
$f_z$ feed [mm]	0,15 ÷ 0,3	0,15 ÷ 0,3	(*)
$a_r$ cutting depth [mm]	2 ÷ 4	2 ÷ 4	(*)

Type of insert	Pre-finishing		
	P10-P20 not coated	P10-P20 coated	HSS
$V_c$ cutting speed [m/min]	140 ÷ 160	180 ÷ 200	(*)
$f_z$ feed [mm]	0,2 ÷ 0,3	0,2 ÷ 0,3	(*)
$a_r$ cutting depth [mm]	< 2	< 2	(*)

Type of insert	Finishing		
	P10-P20 not coated	P10-P20 coated	Cermet P15
$V_c$ cutting speed [m/min]	200 ÷ 240	250 ÷ 270	300 ÷ 340
$f_z$ feed [mm]	0,05 ÷ 0,2	0,05 ÷ 0,2	0,05 ÷ 0,2
$a_r$ cutting depth [mm]	0,5 ÷ 1	0,5 ÷ 1	0,3 ÷ 0,5

(\*) not advisable

## Drilling

Type of insert	tip with interchangeable inserts	HSS	brazed tip
$V_c$ cutting speed [m/min]	130 ÷ 160	(*)	90 ÷ 120
$f_z$ feed per turn [mm/turn]	0,05 ÷ 0,15	(*)	0,15 ÷ 0,25

(\*) not advisable

## General formulae

Type of machining	Drilling	Milling
n: number of turns of mandrel	$V_c * 1000 / \pi * D_c$	$V_c * 1000 / \pi * D_c$
$V_f$ : feed speed [m/min]	$V_f = f_z * n$	$V_f = f_z * n * z_n$
$f_z$ feed per turn [mm/turn]	-	$f_n = V_f / n$
Note	$D_c$ : Milling cutter or tip diameter [mm] $V_c$ : cutting speed [m/min] $f_z$ : feed [mm]	$f_n$ : feed per turn [mm/turn] $z_n$ : No. of milling cutter inserts

## Welding

Welding LUCCHINI 2367 ESR can give good results if it is carried out using the recommended procedure.

As steel with high Carbon Equivalent content, LUCCHINI 2367 ESR is very sensitive to cracking.

We recommend to carry out pre-heating and heat treatment after welding.

In order to obtain the best results, we recommend the following procedure:

<b>Material condition</b>	Annealed	
<b>Welding technique</b>	TIG	MMA
<b>Pre-heating at</b>	330 – 380°C	
<b>Recommended Heat treatment</b>	Heating of the material at 850 °C, cooling in the furnace to 600 °C at a rate of 20 °C/h, cooling at room temperature	
<b>Material condition</b>	Hardened and tempered	
<b>Welding technique</b>	TIG	MMA
<b>Pre-heating at</b>	330 – 380°C	
<b>Recommended Heat treatment</b>	650 °C or 50 °C lower than the tempering temperature previously applied	

## Electrical Discharge Machining (EDM)

Lucchini 2367 ESR can be machined by EDM to obtain complex shape. Afterwards we advise to carry out the stress relieving procedure.

## Process and materials selection for product recyclability

According to the potential of steel recycling, Lucchini RS is adopting a strategy for environmental excellence in designing and manufacturing its tool steel grades, putting eco-effectiveness into practice.

The main adopted steps are:

- to carry out an environmental assessment on processes and products, with the minimum use of virgin materials and non-renewable forms of energy;
- to move toward zero-waste manufacturing processes, considering that the ultimate destination of scrapped steel moulds becomes food for the next steel making process, that is the “waste equals food” philosophy;
- to carry out a life cycle assessment for each product and process, minimizing the environmental cost of product and service over its complete life cycles, from creation to disposal, that is the “Cradle to Cradle” philosophy

Lucchini RS S.p.A. All rights reserved. All contents of this document and all the related industrial and intellectual rights belongs exclusively to Lucchini RS S.p.A. that owns and manages the original version of it. The reproduction, disclosure, dissemination and/or changing of this document, in whole or in part, as well as the utilization of its content and/or the communication there of to third party without express written authorization of Lucchini RS S.p.A. are prohibited.

Via Giorgio Paglia, 45  
24065 LOVERE (BG) - Italy  
Phone +39 035 963724



[www.lucchinirs.com](http://www.lucchinirs.com)

*GROUP*  
**LUCCHINI RS**